



Research Article

Open Access

Photocatalytic Degradation of Dyes using Rutile TiO₂-Pani Composite Prepared by One Pot Method

K. Bharathi Yazhini¹, R. Rajesh Kumar², K. U. Savitha¹, H. Gurumallesh Prabu¹

¹Department of Industrial Chemistry, School of Chemistry, School of Chemical Sciences, Alagappa University, Karaikudi, India- 630003.

²Institute of Advanced Sciences, Education and Research (IASER), Tanjore, India - 613005

Received: 02 June 2015 / Accepted: 28 September 2015

© Science Research Library

Abstract

Anionic dye (Direct Blue1) and cationic (MethyleneBlue) was subjected to degradation under sunlight with synthesized photocatalysts; via anatase TiO₂ (AT), rutileTiO₂ (RT), and rutile TiO₂-polyaniline (RTP) composite. The composite was synthesized by one pot method using TiCl₄ as precursor. The synthesized catalysts were characterized with XRD, FT-IR, UV-Vis and SEM analysis. The dye was degraded and the degree of degradation was calculated. UV-Vis and FT-IR spectra of catalyst loaded with dye were studied with and without sunlight exposure to reveal the photocatalytic action. The %COD removal was also obtained. The results showed that polyaniline can act as sensitizer. A RTP (TiO₂-polyaniline) composition at 1: 0.06 ratios was found to degrade the dye better than all other catalysts. Thus rutile TiO₂ that has lower activity can be made more active than anatase itself by proper compositing with polyaniline. The anionic nature of dye makes it to adsorb on the catalysts. The degradation of the dye can be considered as mainly by adsorption in the absence of sunlight and it competes with catalytic process in the presence of sunlight. The % decolorization and the % COD removal were almost equal and found to be at 60%.

Keywords: TiO₂, Polyaniline, Photocatalyst, Dye, Degradation.

Introduction

TiO₂ is non-toxic, inexpensive, chemically stable, easily available and has excellent photocatalytic performance. Hence, it has received much attention for the detoxification of wastewater. It has emerged as an excellent photocatalyst material for environmental purification. Numerous routes for the synthesis of large and nanosized crystalline TiO₂ particles and films have been developed. These include hydrothermal (Chae et al., 2003), solvothermal (Trentler et al., 1999), sol-gel (Bessekhouad et al., 2003), microwave method (Lin H.Y and Kuo C.Y, 2009), chemical vapor deposition (Chen X and Mao S.S, 2007), electrodeposition (Lei et al., 2001), and other methods (Yu et al., 2001), (Trentler et al., 1999). The formation of anatase is favoured by fast reactions (Wang et al., 2007) and calcination at temperature between 400 and 600 °C (Zhao et al 1998). Calcinations at higher temperature or capillary action (Kim et al 2001) will lead to formation of rutile grade. Anatase grade TiO₂ has a band gap of 3.2 eV and indirect band gaps which prevents the electron- hole recombination. In the case of rutile, the band gap is lower (3 eV), but the recombination occurs fast as it has direct and indirect band gaps. This allows anatase grade to act as better photocatalyst than rutile. The main focus of research going around the world is to make the catalyst active at longer wavelength and to prevent the hole-electron recombination. Conducting polymers like polyaniline (Pani) as sensitizer for TiO₂ and enhanced photocatalytic activity of TiO₂ anatase-Polyaniline composites have been reported (Zhang, 2005, Bitao, 2007, Kim, 2007, Li, 2003). Sulfonated dyes undergo chemical interactions with the charged backbone of Pani,

*Corresponding author: hgrabu2010@gmail.com



leading to significant adsorption of the dyes (Mahanta et al., 2008).

In this study, rutile TiO₂ is composited with pani (RTP) using one pot synthesis method and photocatalytic efficiency is compared with anatase grade TiO₂.

Materials and methods

Titanium tetrachloride and Hydrazine hydride were purchased from Loba chemicals. Aniline (CDH) was purified by distillation before use. Ammonium persulfate and hydrochloric acid were obtained from Fisher India Ltd, and used without further purification. The dyes Direct blue 1 (DB1), Methylene blue (MB), was purchased from Nice & Atul Ltd respectively and used as model pollutants.

The Molecular Formula of Direct blue 1 (DB1) dye is C₃₄H₂₄N₆Na₄O₁₆S₄, CAS Number is 2610-05-1 and the colour Index Number is 24410. Its IUPAC name is Tetra sodium (6E)-4-amino-6-[[4-[4-[N⁻(8-amino-1-oxo-5,7-Disulfonato-2 naphthylidene)hydrazine]-3-methoxy-phenyl]-2-methoxy-phenyl] hydrazono]-5-oxo-naphthalene-1,3-disulfonate.

The Molecular Formula of Methylene blue (MB) dye is C₁₆H₁₈CN₃S₃.3H₂O CAS Number is 61-73-4 and the colour Index Number is 52015. Its IUPAC name is 3, 7-Bis dimethylamino-phenothiazin -5-iumchloride.

Instruments used: UV-Vis spectra were recorded using JASCO-V-530 spectrophotometer. FT-IR spectra were recorded using SHIMADZU 8400S spectrophotometer. XRD analysis was performed using XPERT PANALYTIC. The particle size and morphology of the composite were examined by scanning electron microscope (SEM) HITACHI S300H. Dye degradation percentage was analyzed using MERCK Thermoreactor COD analyzer.

Preparation of catalysts

- **Preparation of anatase TiO₂ (AT):** 5 ml of titanium tetrachloride was dissolved in 10 ml of hydrochloric acid with constant stirring for 2 hours at cooling condition. 40 ml of distilled water was added drop wise. Then 3M hydrazine hydride was added drop wise under vigorous stirring for 1 hour. The precipitate thus obtained was filtered and dried over night and then calcination was carried out at 500°C for 2 hours.
- **Preparation of rutile TiO₂ (RT):** 2 ml of titanium tetrachloride was dissolved in 10 ml of alcohol and 34 ml of 1M hydrochloric acid was added. Yellow gel was obtained which turned colorless on addition of hydrochloric acid and heated with constant stirring for 4 hours. White precipitate was obtained. It was filtered and washed with distilled water and dried.
- **Preparation of Pani:** Pani was prepared by chemical polymerization of aniline. About 5 ml of aniline was dissolved in 34 ml of 1M hydrochloric acid with constant stirring at ice-cold condition. Then 10 g of ammonium persulfate was dissolved in 5 ml of hydrochloric acid and added drop wise to the above solution at 0°C. The solution was stirred vigorously.

The Green precipitate thus obtained was washed with hot water, ethanol and then dried.

- **Preparation of rutile TiO₂ - Pani (RTP):** 4 ml of titanium tetrachloride was dissolved in 10 ml of alcohol taken in a beaker. 5 ml of aniline dissolved in 34 ml of 1M hydrochloric acid was added drop wise with constant stirring. Yellow gel was obtained which turned colorless on addition of hydrochloric acid. Stirring was continued for 4 hours. Then nitrogen gas was passed for 5 minutes, sealed to make the inert atmosphere of Nitrogen inside. Then 1.6 g of ammonium persulfate dissolved in 5 ml of hydrochloric acid was injected at ice-cold condition. The system was stirred vigorously for 2 hours and kept overnight for the completion of reaction. The Green precipitate thus obtained was then filtered. This process was repeated with 0.5, 0.1 and 0.03 ml of aniline to get TiO₂-Pani composites at different ratios such as 1:0.1, 1:0.06 and 1:0.02 respectively.

Dye degradation

Known amount of the dye was added with different catalyst separately and subjected to direct sunlight exposure for 30 min in noon time. Similar control system was kept in dark for 30 min to study the effect of adsorption. Then all test solutions were centrifuged and catalyst was removed. The optical density of dye solution before and after catalytic treatment was noted and compared. The results obtained with polyaniline, pure TiO₂ (both anatase and rutile) and different polyaniline/TiO₂ ratio were compared. The effects of dye concentration, catalyst loading and pH were studied.

COD analysis

The chemical oxygen demand (COD) of the test sample was measured using thermoreactor TR 200 (Merck) with COD solution A and COD solution B. In this analysis, 0.03 ml of COD solution A (Art.no1.14538) and 2.30 ml of COD solution B (Art.no1.14680) were taken in a cell and mixed. Then 3 ml of solution to be tested was added to the cell and the lid was closed. The cell content was digested using thermoreactor at 148°C for 2 hours. In another cell, 0.30 ml of COD solution A and 2.30 ml of COD solution B were taken, 3ml of pure distilled water was added to it and the lid was closed and digested, which was considered as blank sample. Then the cells were cooled down to ambient temperature and the absorbance of this solution was measured at a wavelength of 585 nm against the blank and multiplied with a factor 1636 to get the COD value in ppm.

Result and Discussion

XRD analysis

The average particle size of the composites synthesized was calculated from Scherrer's formula. The average particle sizes were found to be 14 and 22 nm respectively for anatase and rutile forms respectively. The hydrolysis reaction of TiCl₄ in HCl and ethanol may be in two different routes. The mechanisms proposed in the literature explain that TiCl₄ in HCl undergo hydrolysis yielding TiO₂.nH₂O, which on calcination gives anatase TiO₂ depending upon calcinating

temperature and time, whereas TiCl₄ in ethanol yields TiO₂ on reacting in the following path way.

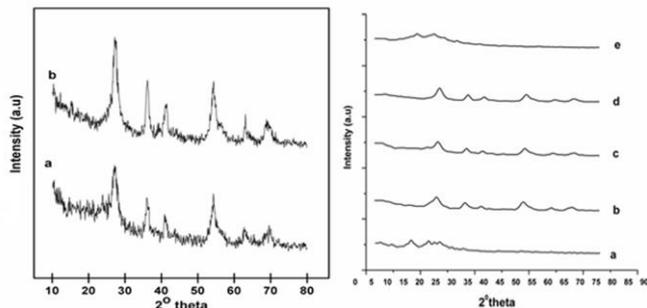





Fig.1

XRD pattern of TiO₂.
(a = AT, b = RT).

XRD patterns of RTP
composites at different ratios
(a = 1:1, b = 1:0.1, c = 1:0.06, d
= 1:0.02, e = pristine Pani)

FT-IR analysis

The FT-IR spectra of Pani and Pani-TiO₂ clearly show the formation of composite. In the latter, the characteristic bands of PANI appeared and obviously shifted to the lower wavenumber. The main characteristic bands of Pani are assigned as follows: The peak at 3419 cm⁻¹ is attributed to N-H stretching mode. Peaks at 1562 cm⁻¹ and 1479 cm⁻¹ are associated for C=N and C=C stretching mode for the quinonoid and benzenoid rings.

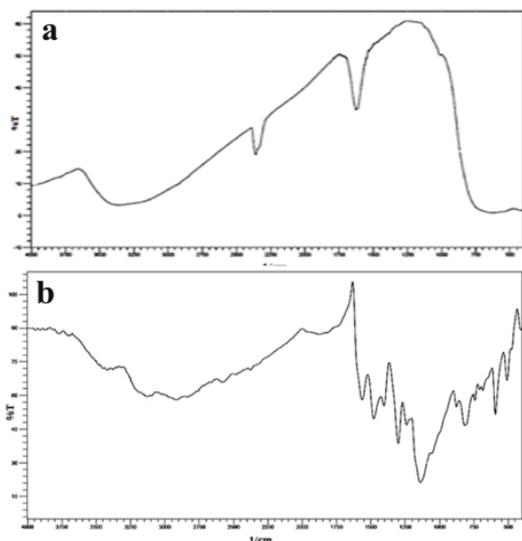


Fig.2

a. FT-IR spectrum of TiO₂ (RT)
b. FT-IR spectrum of Pani

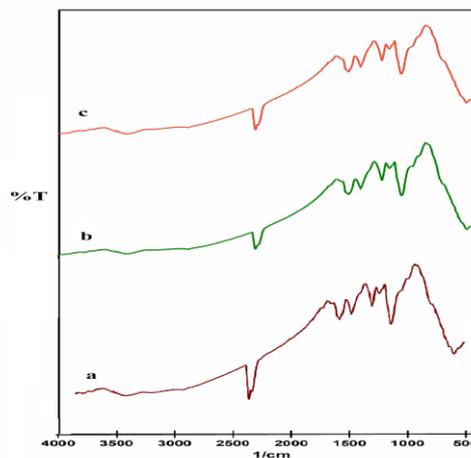


Fig.3

a. FT-IR spectrum of RTP composite
b. RTP composite after treating with dye in sunlight
c. RTP composite after treating with dye in dark

Peaks at 1300 cm⁻¹ and 1240 cm⁻¹ can be attributed to C-N stretching mode for benzenoid ring. Peak at 1141 cm⁻¹ is due to quinonoid unit of doped Pani. Peak at 815 cm⁻¹ is usually assigned to an out-of-plane bending vibration of C-H of 1, 4 substituted benzenoid rings, which confirmed the formation of Pani. The intensities of some peaks, for example 3419, 1562, 1058 and 815cm⁻¹ are affected by the presence of TiO₂ in Pani synthesis. These differences in the IR spectra can be explained on the basis of constrained growth and restricted modes of vibrations in Pani grown in the presence of TiO₂. In such case, aniline monomer gets adsorbed onto the oxide particles, which were dispersed in the reaction mixture and polymerization proceeds initially on the surface of these oxide particles when ammonium persulfate was added to the solution. This leads to adhesion of the polymer to the TiO₂ particles and the constrained growth around these particles. Such adsorption and constrained motion of the chains lead to the differences. The finer size of the particles can also give rise to sharpness of the peaks in the IR spectra giving better resolution of the bands.

SEM analysis

SEM results show that pristine TiO₂ is of nanometer in size with two dimensional branched structures. The SEM image of Pani is given below. The SEM image of the TiO₂-Pani composite prepared has flake like structures arranged one above the other. The polymer growth is above the semiconductor particles giving TiO₂ fully embedded in polymer matrix. The EDAX results show the presence of titanium in TiO₂ - Pani.

UV-Visible spectral analysis

The UV-visible spectra of pristine TiO₂ (RT) and RTP composite are given. It is clear from the spectra that the absorption range of TiO₂ is red shifted in the composite. Hence the Pani sensitizes TiO₂ to the visible region and influences the activation under the visible light.

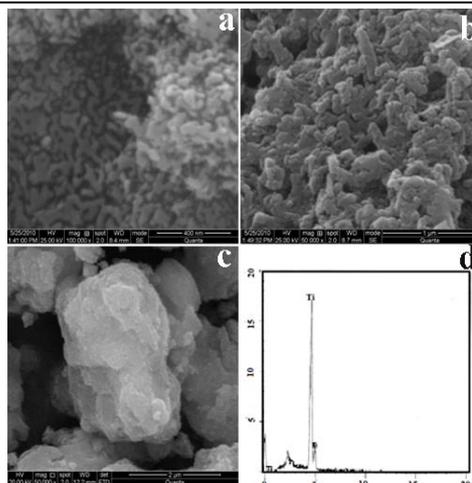


Fig.4

- a. TiO₂ (RT)
- b. Pani
- c. RTP composite
- d. EDAX of Pani TiO₂ composite

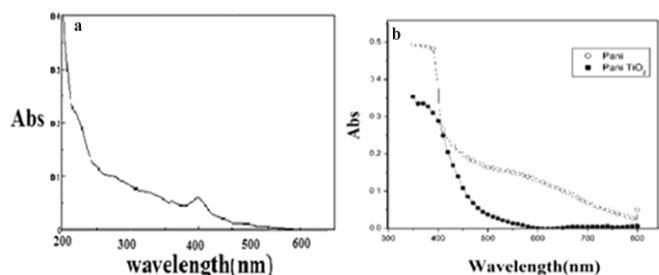


Fig.5


- a. pristine TiO₂
- b. RTP composite and pristine Pani

Catalytic degradation of DB1 dye

It can be inferred from the table that MB is not adsorbed while DB1 is greatly adsorbed to the catalyst. The degradation of DB1 can be considered as adsorption only and on sunlight exposure, it competes with catalytic process. The decrease in degradation percentage with 1:1 ratio of TiO₂-PANI may be explained as the result of desorption due to the competition.

Catalyst (grams)	% Dye degradation			
	With sunlight exposure		Without sunlight exposure	
	MB	DB1	MB	DB1
TiO ₂ anatase	61.14	33.31	15.28	12.87
TiO ₂ Rutile	50.29	23.25	3.85	19.02
1:1 (TiO ₂ -PANI)	18.61	35.25	8.85	93.45
1:0.1 (TiO ₂ -PANI)	50.81	85.19	37.35	89.19
1:0.06 (TiO ₂ -PANI)	69.29	89.34	14.54	88.03
1:0.02 (TiO ₂ -PANI)	29.83	59.03	15.54	40.94

The mechanism of adsorption of anionic dyes on PANI explained by (D.Mahantha et al., 2008) also supports this observation. The SO₃⁻ group on the dye could lead to chemical interactions with the positively charged backbone of PANI emeraldine salt, and Na⁺ ions interact with the chloride ions that are invariably present in doped PANI. This will lead to the adsorption of various sulfonated dyes on the emeraldine salt of PANI. In basic aqueous solutions (dispersion of emeraldine base in water), the dissociation of the functional group of the dye would be inhibited, and no chemical interaction with the PANI backbone would be expected. But in the case of composites, the TiO₂ core acts as negative centre and so when activated by sunlight, the electrons will be provided by TiO₂. At lower concentration of PANI, the adsorption takes places in the dark and catalysis exceeds it in presence of sunlight.

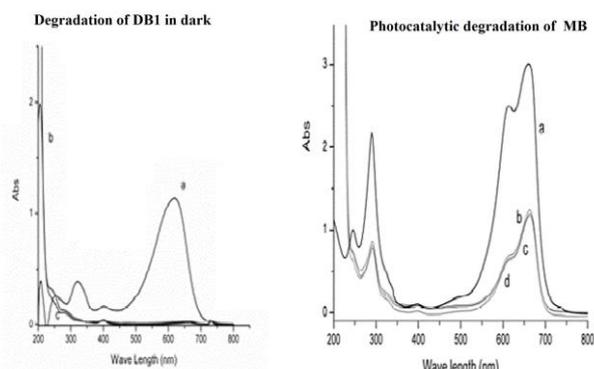

The degradation of DB1 in dark with 1:1 TiO₂-PANI composite. It shows about 90% adsorption

The photocatalytic degradation of MB with 1:0.6 ratio of composite.

Fig.6

The curves a, b, c, d represents the time of irradiation for degradation at 15, 30, 45 and 60 minutes respectively. The prolonged irradiation has no effect. This may be due to the catalytic action may come to equilibrium after a period of time.

The fig.6 a and 6 b show the absorption spectra of composite catalyst used for DB1 and MB in sunlight and dark. In the case of DB1, the adsorption takes place in dark (Abs at 600-700nm region is 0.05 a.u) and photocatalytic activity and desorption in light leaving behind sensitized catalyst over the entire visible area (Abs at UV region increases to maximum showing degradation of adsorbed materials and revealing the property of catalyst). In the case of MB, the adsorption is not taking place and in the sunlight and the degraded product of MB is adsorbing on the catalyst.

Catalyst loading

The catalyst loading effect in sunlight and dark reactions work in similar manner. The initial increase and then decrease may be due to the decrease in available surface area at higher concentration

Effect of pH

The effect of pH is similar in the case of MB for dark and sunlight reaction but reverse with DB1. This may be due to the fact that in DB1, the mechanism of sunlight and dark reaction is different.

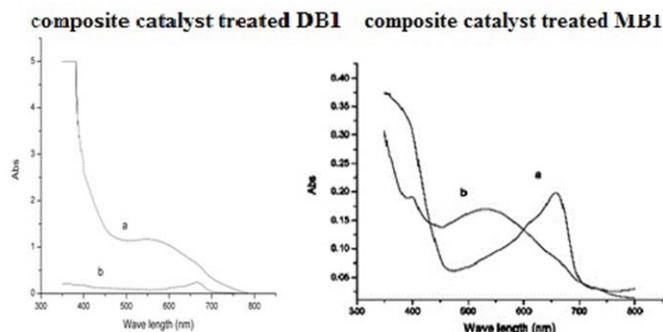


Fig.7

a. In sunlight b. In dark

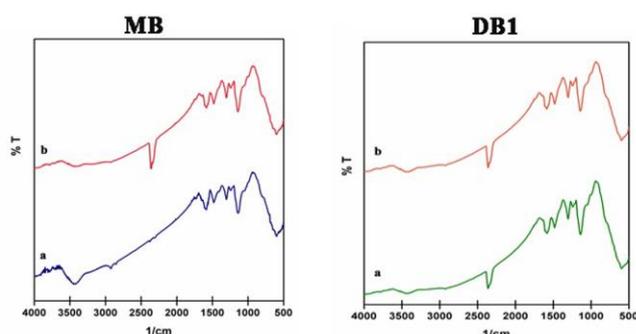


Fig.8

The following FT-IR results of the catalysts used for DB1 and MB in dark and sunlight (figures 8) also supports the adsorption and photocatalytic mechanism explained above.

Parameter studies

Dye concentration

Increase in dye concentration from 0.1 to 0.5 % decreases the dye degradation. This may be due to the lower availability of catalytic at those concentrations

COD analysis

The COD analysis shows the degradation efficiency (ppm removal) of MB and DB1 as 62 and 60% respectively, which supports the conclusion that photocatalysis occurred for DB1 in the presence of sunlight.

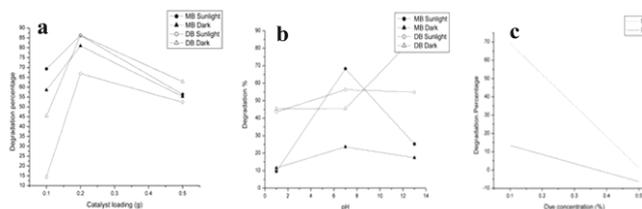


Fig.9

- 0.1M dye concentration, 30 min interval at pH 7
- 0.1g of catalyst with 0.1 M dye concentration at 30 min interval
- 0.1 to 0.5 dye concentration

Conclusion

RTP composite acted as better photocatalyst than all other catalyst studied. RTP at ratio 1: 0.6 showed better dye degradation efficiency than other ratios. In our study, it is concluded that the process is adsorption in dark and photocatalysis in the presence of light. The anionic dye adsorbs in dark and undergoes photocatalytic reaction in presence of sunlight. The percentage degradation was higher with cationic dye (MB) than with anionic dye (DB1).

References

- Bessekhouad, Robert Y and Weber D (2003). Synthesis of photocatalytic TiO₂ nanoparticles: optimization of the preparation conditions. *J. Photochem. Photobiol. A*, 157:47.
- Bitao S.U, Shixiong M.I.N, Shixiong S.H.E, Yongchun T and Jie B (2007) Synthesis and characterization of conductive polyaniline/TiO₂ composite nanofibers. *Front.Chem.China*, 2:123-126
- Chae S, Park Y, Lee M.K, Kim S.K, Kim T.Y and Lee S.K (2003). Preparation of Size-Controlled TiO₂ Nanoparticles and Derivation of Optically Transparent Photocatalytic Films. *Chem. Mater*, 15: 3326.
- Chen X and Mao S.S (2007) Titanium dioxide nanomaterials: synthesis, properties, modifications, and applications. *Chem.Rev.* 107:2891-2959
- Kim J.Y, Lee J.H and Kwon S.J (2007) The manufacture and properties of polyaniline nano-films prepared through vapor-phase polymerization. *Synth Met*, 2007, 157:336-34.
- Kim S.J, Lee E.G, Park S.D, Jeon C.J, Cho Y.H, Rhee C.K and Kim W.W (2001) Photocatalytic Effects of Rutile Phase TiO₂ Ultrafine Powder with High Specific Surface Area Obtained by A Homogeneous Precipitation Process at Low Temperatures. *J.Sol-GelSci.Technol*, 22, 63-74.
- Lei Y, Zhang L and Fan D, J. C. (2001) Fabrication, characterization and Raman study of TiO₂ nanowire arrays prepared by anodic oxidative hydrolysis of TiCl₃. *Chem. Phys. Lett.*, 338: 231.
- Li X, Chen W, Bian C, He J, Xu N and Xue G (2003) Surface modification of TiO₂ nanoparticles by polyaniline. *Appl.Surf.Sci.* 217:16-22.
- Lin H.Y and Kuo C.Y (2009) Photocatalytic activity of TiO₂ prepared by microwave/sol-gel method. *React Kinet Catal Lett*, 98 :241-247.
- Mahanta D, Madras G, Radhakrishnan S and Patil S (2008) Adsorption of Sulphonated Dyes by Emeraldine Salt

- Polyaniline and its Kinetic Study. *J.Phys.Chem.B*, 112: 10153-10157.
- Trentler T.J, Denler T.E, Bertone J.F, Agrawal A and Colvin V.L (1999) Synthesis of TiO₂ nanocrystals by nonhydrolytic solution-based reactions, *J.Am.Chem.Soc*, 121:1613-1614.
- Trentler T.J, Denler T.E, Bertone J.F, Agrawal A and Colvin V.L (1999). Synthesis of TiO₂ nanocrystals by nonhydrolytic solution-based reactions. *J.Am.Chem.Soc*, 121: 1613-1614.
- Wang Y, Zhang L, Deng K, Chen X and Zou Z (2007) Low Temperature Synthesis and Photocatalytic Activity of Rutile TiO₂ Nanorod Superstructures. *J.Phys.Chem.C*, 111:2709-2714.
- Yu J.C, Yu J, Ho W and Zhang L (2001) Preparation of highly photocatalytic active nano-sized TiO₂ particles via ultrasonic irradiation. *Chem.Commun*, 13:194
- Zhang L, Wan M, Wei Y (2005) Polyaniline/TiO₂ microspheres prepared by a template free method. *Synth Met*, 151:1-5
- Zhao G, Utsumi S, Kozuka H, Yoko T, J (1998) Photoelectrochemical properties of sol-gel-derived anatase and rutile TiO₂ films. *Mater. sci*, 1998, 33:3655-3659



Science Research Library (SRL) Open Access Policy

SRL publishes all its journals in full open access policy, enables to access all published articles visible and accessible to scientific community.

SRL publishes all its articles under Creative Commons Attribution - Non-Commercial 4.0 International License



Authors/contributors are responsible for originality, contents, correct references, and ethical issues.

Author benefits:

- ✓ Online automated paper status
- ✓ Quality and high standards of peer review
- ✓ Rapid publication
- ✓ Open Access Journal Database for high visibility and promotion of your research work
- ✓ Inclusion in all major bibliographic databases
- ✓ Access articles for free of charge